

The Use of Atomic Force Microscopy in Determining the Stiffness and Adhesion Force of Human Dentin After Exposure to Bleaching Agents

Leopoldo Forner, MD, DDS, PhD,* Manuel Salmerón-Sánchez, PhD,[†] María Palomares, DDS,* Carmen Llena, MD, DDS, PhD,* and José Amengual, MD, DDS, PhD*

Abstract

Introduction: Oxidant bleaching agents may induce several alterations on mineralized teeth tissues. Our aim is to study, at the ultrastructural level, mechanical modifications induced on dentin after exposure to different bleaching agents. **Methods:** Nanoindentation performed with atomic force microscopy was used to measure changes in dentin stiffness as well as the adhesion force between the tip and the tissue both in intertubular and peritubular dentin. For each specimen, dentin localization, and bleaching agent, 100 independent nanoindentations were performed. Carbamide peroxide (30%) and hydrogen peroxide (35%) were used as bleaching agents. **Results:** A significant reduction of both stiffness and adhesion force was found for both carbamide and hydrogen peroxide in peritubular and intertubular dentin. **Conclusions:** The use of bleaching agents led to a significant reduction in dentin local (at the nanoscale) mechanical properties. (*J Endod* 2009;35:1384–1386)

Key Words

Atomic force microscopy, carbamide peroxide, dental bleaching, hydrogen peroxide, intertubular dentin, nanoindentation

From the *Department of Stomatology, Universitat de València, Valencia, Spain; and [†]Center for Biomaterials and Tissue Engineering, Universidad Politécnica de Valencia, 46022 Valencia, Spain.

Address requests for reprints to Dr Leopoldo Forner, Department of Stomatology, Universitat de València, Estomatología, C. Gascó Oliag, 1 46010Valencia, Valencia, Spain. E-mail address: forner@uv.es.

0099-2399/\$0 - see front matter

Copyright © 2009 American Association of Endodontists. doi:10.1016/j.joen.2009.06.023

Commercial products commonly used as bleaching agents are based on hydrogen and carbamide peroxides (H_2O_2 and $CO(NH_2)_2 \cdot H_2O_2$, respectively). Hydrogen peroxide dissociates into free radicals, which perform their bleaching action through the oxidation of complex chromogenic molecules. On the other hand, carbamide peroxide decomposition gives rise to hydrogen peroxide that is, in the end, responsible for the final effect. However, superimposed onto the therapeutic effects, these oxidant agents may show deleterious effects that include alterations in the structure of teeth mineralized tissues (1–3); in any case, these alterations have not been found for low concentrations of the bleaching agent (eg, carbamide peroxide 10%, and hydrogen peroxide 3.5%) (4, 5). The dentin can be modified during internal bleaching in endodontically treated teeth; these alterations include modifications in Ca and P concentrations (6), increased roughness with acid etching appearance (7), alterations in the organic and inorganic phases of dentin (8), and hardness reduction (9, 10). These alterations are important because they may lead to weakening of the dental structure to biomechanical solicitations (10). There are only a few works that employ atomic force microscopy (AFM) to investigate alterations in teeth mineralized tissues (11–13) and are mainly focused on nanostructural modifications in enamel and intertubular dentin.

This work aims to investigate modifications at the nanostructural level in dentin, both peritubular and intertubular, induced by the application of the following high concentration bleaching agents: hydrogen peroxide 35% and carbamide peroxide 30%.

Materials and Methods

Ten sections containing both dentin and enamel were obtained from 10 first molars without carious lesions extracted by periodontal reasons and with an intact coronal structure transversely cut in 1-mm thickness slices. The section surface was polished by a set of abrasive discs of decreasing gradient in a polisher (SBT 900; South Bay Technology, Arlington, VA) with water refrigeration; afterwards, they were polished with diamond dust. Finally, samples were washed in an ultrasonic bath with distilled water for 20 minutes.

Samples were randomly distributed into two groups for the different treatments. Bleaching agents used were 30% carbamide peroxide (Vivastyle; Ivoclar/Vivadent, Schaan, Liechtenstein) and 35% hydrogen peroxide (PolaOffice; SDI, Victoria, Australia); they were applied using the following manufacturer recommendations: 3 applications of the bleaching agent for 30 minutes in the first case and 8 minutes in the second one. Each sample was treated with only one bleaching agent.

Nanoindentation experiments were performed in a NanoScope III Atomic Force Microscope (Digital Instruments, Santa Barbara, CA). A square pyramidal tip OTR8 (Veeco, Plainview, NY) with a spring constant 0.57 N/m (datum supplied by the manufacturer) and a tip half angle of 35° was used. Calibration of the tip sensitivity was performed in the same conditions as the experiments with a flat surface sample made of the same material as the tip and was calculated to be -5.721 nm/V after at least 10 repetitions (14). Sensitivity of the tip was used to correct the deflection of the tip caused by the vertical movement of the sample without penetration.

Samples for indentation experiments were sheets, around 1-mm thick, glued on a stiff surface. All experiments were performed with the instrument mounted on a vibration isolation system. Measurements were performed before and after the

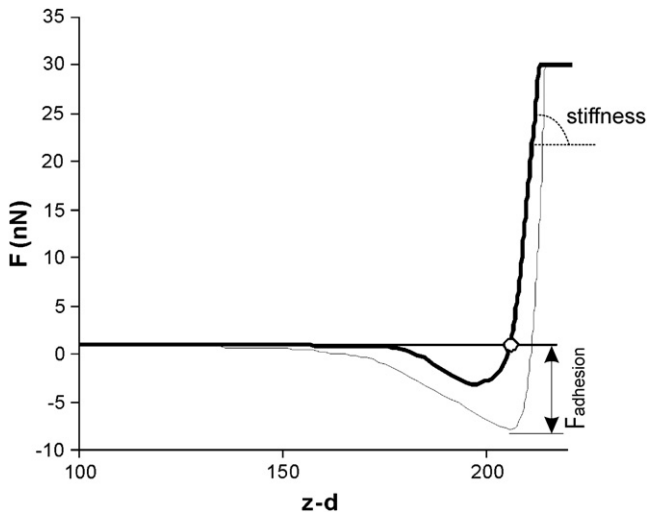


Figure 1. An example of a measured curve in an indentation AFM experiment; force versus the difference between the z displacement of the sample and the cantilever deflection d is shown. The thick line represents the indentation scan and the thin one the retraction one. Stiffness is calculated from the uploading curve and the adhesion force from the downloading one.

treatment both in intertubular and peritubular dentin. Nanoindentation experiments allow one to get information about the local mechanical properties of the system. The result of one of these experiments is shown in Figure 1, where the force is represented against the difference between the displacement of the sample in the vertical axis, z , and the cantilever deflection, d . The variable $z - d$ is the relative displacement between the tip and the sample surface. At low values of $z - d$, there is no contact between the tip and the surface (both the deflection of the cantilever and the measured force are near zero). The thick line (Fig. 1) is obtained during indentation, whereas the thin one corresponds to the retracting scan. The negative values of the force (attraction force between the tip and the surface because of van der Waals long-range interactions) are produced close to the contact point (15), which can be determined using the extrapolation shown in Figure 1 (ie, it is the intersection point between the experimental curve and the horizontal reference assumed for absence of contact). For greater values of relative displacement ($h = z - d$), short-range repulsive interactions take place between the sample and the tip as well as the indentation of the material, which overcome the previous attraction forces making the force F to increase. Ascribing the value of penetration zero to this point, the plot in Figure 1 can be transformed into a force-penetration graph. The adhesion force between the tip and the sample can be calculated from the minimum of the retracting curve. The stiffness S is then defined as the slope of this graph

$$S = \frac{\partial F}{\partial h}$$

In an elastic body, S can be related to the elastic modulus and the hardness (16), but for the purposes of this work, an analysis of the stiffness itself throughout the sample surface is sufficient. In fact, the stiffness can be calculated as

$$S = \frac{\partial F}{\partial(z - d)}$$

Indentation experiments were performed in every sample (after different treatments) in 100 points located on a 10×10 matrix with

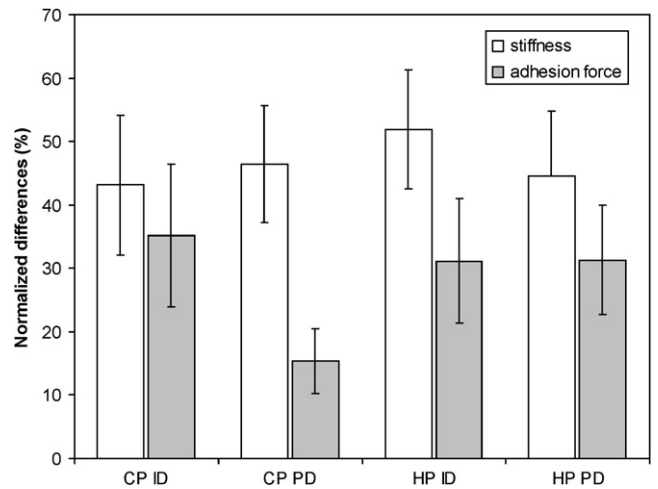


Figure 2. Normalized differences (percentage) for stiffness and adhesion force before and after bleaching treatments on peritubular and intertubular dentin. CP, carbamide peroxide; HP, hydrogen peroxide; ID, intertubular dentin; PD, peritubular dentin. White columns: before bleaching, gray columns: after bleaching.

rows and columns separated 10 nm from each other. Thus, the stiffness is measured over a square of $1 \times 1 \mu\text{m}$. The nanoindentation area was selected after several imaging steps for every specimen. First, a region with homogeneously distributed dentin tubules (free of defect or impurities) was selected by using an optical microscopy ($400\times$) coupled to the AFM. Afterwards, several images of increasing resolution were acquired (AFM) until a single dentin tubule in a $5 \times 5 \mu\text{m}$ area was visualized. The nanoindentation areas (intertubular and peritubular dentin) were finally selected from this high-resolution image. Nanoindentation experiments provide the adhesion force and the stiffness for each sample as the mean value of 100 points. These measurements allow one to assess adhesion force and stiffness.

Results

The adhesion force and the stiffness were initially calculated for each sample as previously explained. Afterwards, bleaching treatments were applied (five with carbamide peroxide and five with hydrogen peroxide) and adhesion force and stiffness were immediately measured in new AFM experiments. The normalized difference (N_D , relative to the untreated value) between this magnitude before and after treatment were accordingly calculated in order to compare the effect of the treatment for the different specimens regardless of the absolute values of these magnitudes using the following equation:

$$N_D = \frac{S_b - S_a}{S_b}$$

S_a and S_b are the magnitudes (either adhesion force or stiffness) after and before the bleaching treatment, respectively. Accordingly to this, Figure 2 represents the mean value (five specimens) of the N_D for both stiffness and adhesion force. A significant reduction of approximately 50% is found for each bleaching agent (carbamide peroxide and hydrogen peroxide) irrespective of the application area (intertubular dentin and peritubular dentin) without differences among them. Similar trends are observed for the adhesion force, but the reduction in adhesion force is lower for carbamide peroxide applied on peritubular dentin.

Discussion

Two commercial bleaching products were selected in this work, which were applied by following the guidelines of the manufacturer. Both products, hydrogen peroxide and carbamide peroxide, were used in high concentrations as in clinical procedures, taking into account that peroxide carbamide 30% is equivalent to hydrogen peroxide 10% (17).

Several works have investigated the microhardness of mineralized dental tissues, mainly enamel, with contradictory results. In a recent review (18), it is argued that variability among results might be a consequence of the procedure followed to maintain teeth in between applications of the product. In our case, the application of bleaching agents was performed immediately after washing the previously applied agent. AFM experiments were performed after the last application. Besides, microhardness reductions have been described in dentin after contacting bleaching agents, both in low concentration, carbamide peroxide 10% (19), and high concentration, carbamide peroxide 30% (20), as well as significant changes in microroughness (21). Nevertheless, other authors have found no significant changes with hydrogen peroxide 35% for 2 hours (22) or hydrogen peroxide 35% for 30 minutes or 30% for 24 hours (23). The addition of chlorhexidine as the antimicrobial agent during bleaching did not influence dentin microhardness (24).

Nanoindentation studies have also shown a reduction in dentin hardness (25, 26) as well as in the Young modulus after bleaching treatments (25). Only intertubular dentin was analyzed in these works by performing eight indentations per sample. We have investigated both intertubular and peritubular dentin, and, moreover, we have performed 100 (nano)indentations for each treatment and sample because of the nanometric character of our methodology. It is important to remark here that the error bars shown on each graph (Fig. 2) represent the standard deviation for the normalized difference for stiffness and adhesion force before and after bleaching treatments on peritubular and intertubular dentin for five specimens. That is to say, the comparison between 1,000 indentation curves (500 before and 500 after treatment) is included, which strengthens the reliability of our methodology as compared with standard indentation experiments.

Peritubular dentin is known to be compact and regular compared with the intertubular one, which is less regular and granular-like (27), with higher magnesium and whitlockite contents (28). Both peritubular and intertubular dentin consist of carbonated apatite, which differs in collagen and protein composition (29). We have identified a generalized loss of stiffness and adhesion force after applying any of the bleaching agents and for every dentin zone. Mechanical dentin modifications produced by bleaching agents could lead to biomechanical alterations, but there is no evidence to substantiate this (30). In the same way, clinical consequences are unknown (31). However, further studies are needed to investigate these alterations, which might give rise not only to clinical manifestations in the biomechanical properties of teeth but also in adhesion mechanisms of resins to dentin after bleaching treatments. Probably, new bleaching techniques (32) could improve both efficacy and safety.

References

1. Bitter NC. A scanning electron microscopy study of the effect of bleaching agents on enamel: a preliminary report. *J Prosthet Dent* 1992;67:852–5.
2. Lena MC, Forner L, Fernández A, et al. Effects de deux agents pour blanchissement sur le surface de l'email. Etude in vitro. *Bull Group Int Rech Sci Stomatol et Odontol* 1992-93;3-4:117–120.

3. Josey AL, Meyers IA, Romaniuk K, et al. The effect of a vital bleaching technique on enamel surface morphology and the bonding of composite resin to enamel. *J Oral Rehabil* 1996;23:244–50.
4. McCracken MS, Haywood VB. Effects of carbamide peroxide on the surface hardness of enamel. *Quintessence Int* 1995;26:21–4.
5. Berga A, Forner L, Amengual J. In vivo evaluation of the effects of 10% carbamide peroxide and 3,5% hydrogen peroxide on the enamel surface. *Med Oral Patol Oral Cir Bucal* 2007;12:E404–7.
6. Rotstein I, Dankner E, Goldman A, et al. Histochemical analysis of dental hard tissues following bleaching. *J Endod* 1996;22:23–5.
7. Zalkind M, Arwaz JR, Goldman A, et al. Surface morphology changes in human enamel, dentin and cementum following bleaching: a scanning electron microscopy study. *Endod Dental Traumatol* 1996;12:82–8.
8. Cimilli H, Pameijer CH. Effect of carbamide peroxide bleaching agents on the physical properties and chemical composition of enamel. *Am J Dent* 2001;14:63–6.
9. Lewinstein I, Hirschfeld Z, Stabholtz A, et al. Effect of hydrogen and sodium perborate on the microhardness of human enamel and dentin. *J Endod* 1994;20:61–3.
10. Ernst CP, Marroquin BB, Willershausen B. Effects of hydrogen peroxide containing bleaching agents on the morphology of human enamel. *Quintessence Int* 1996;27:53–6.
11. Hegedüs C, Bistey T, Flóra-Nagy E, et al. An atomic force microscopy study on the effect of bleaching on enamel surface. *J Dent* 1999;27:509–15.
12. Chng HK, Ramli HN, Yap AUJ, et al. Effect of hydrogen peroxide on intertubular dentine. *J Dent* 2005;33:363–9.
13. Hairul BR, Lim CT, Chng HK, et al. Nanoindentation study of human premolars subjected to bleaching agent. *J Biomech* 2005;38:2204–11.
14. González C, Latorre L, Moratal D, et al. Poly(L-lactide) substrates with controlled surface chemistry by plasma copolymerization of acrylic monomers. *Plasma Process Polym* 2009;6:190–8.
15. Drelich J, Xu Z, Masliyah J. Structural effects recorded for AFM tips interacting with individual nanoparticles and their clusters deposited on substrates. *Langmuir* 2006;22:8850–9.
16. Hues SM, Draper CF. Nanoindentation. In: Colton RJ, Engel A, Frommer JE, et al., eds. *Procedures in scanning probes microscopies*. Hoboken NJ: John Wiley & Sons; 1999:585.
17. Plotino G, Buono L, Grande NM, et al. Nonvital tooth bleaching: a review of the literature and clinical procedures. *J Endod* 2008;34:394–407.
18. Atin T, Muller T, Patyk A, et al. Influence of different bleaching systems on fracture toughness and hardness of enamel. *Op Dent* 2004;29:188–95.
19. Dadoun MP, Bartlett DW. The microhardness of bleached dentine and its bond strength to a dentin bonding agent. *Eur J Prosthodont Restor Dent* 2007;15:131–4.
20. Pecora JD, Cruz-Filho AM, Sousaneto MD, et al. In vitro action of various bleaching agents on the microhardness of human dentin. *Braz Dent J* 1994;5:129–34.
21. Markovic L, Jordan RA, Lakota N, et al. Micromorphology of enamel surface after vital tooth bleaching. *J Endod* 2007;33:607–10.
22. Sulieman M, Addy M, MacDonald E, et al. A safety study in vitro for the effects of an in-office bleaching system on the integrity of enamel and dentine. *J Dent* 2004;32:581–90.
23. Al-Salehi SK, Wood DJ, Hatton PV. The effect of 24 h non-stop hydrogen peroxide concentration on bovine enamel and dentine mineral content and microhardness. *J Dent* 2007;35:845–50.
24. De Oliveira DP, Nogueira EC, Randi CC, et al. Effect of intracoronal bleaching agents on dentin microhardness. *J Endod* 2007;33:460–2.
25. Chng HK, Ramli HN, Yap AU, et al. Effect of hydrogen peroxide on intertubular dentin. *J Dent* 2005;33:363–9.
26. Hairul Nizam BR, Lim CT, Chng HK, et al. Nanoindentation study of human premolars subjected to bleaching agent. *J Biomech* 2005;38:2204–11.
27. Costa L, Watabe I-S, Kronka M, et al. Structure and microstructure of coronary dentin in non-erupted human deciduous incisor teeth. *Braz Dent J* 2002;13:170–4.
28. Frank RM. Ultrastructure of human dentine 40 years ago—progress and perspectives. *Arch Oral Biol* 1999;44:979–84.
29. Weiner S, Veis A, Beniash E, et al. Peritubular dentin formation: crystal organization and the macromolecular constituents in human teeth. *J Struct Biol* 1999;126:27–41.
30. Chng HK, Palamara JE, Messer HH. Effect of hydrogen peroxide and sodium perborate of biomechanical properties of human dentin. *J Endod* 2002;28:62–7.
31. Tam LE, Abdool R, El-Badrawy W. Flexural strength and modulus properties of carbamide peroxide-treated bovine dentin. *J Esthet Restor Dent* 2005;17:359–67.
32. Lee HW, Kim GJ, Kim GM, et al. Tooth bleaching with nonthermal atmospheric pressure plasma. *J Endod* 2009;35:587–91.